

# Plastics — Determination of tensile properties —

## Part 1: General principles

The European Standard EN ISO 527-1:1995 has the status of a British Standard

**IMPORTANT NOTE.** Before reading this method it is essential to read BS 2782-0 *Introduction*, issued separately.

ICS 83.080

## Committees responsible for this British Standard

The preparation of this British Standard was entrusted by the Plastics and Rubber Standards Policy Committee (PRM/-) to Technical Committee PRM/21, upon which the following bodies were represented:

British Plastics Federation  
 British Textile Confederation  
 Department of the Environment (Building Research Establishment)  
 Department of Trade and Industry (National Physical Laboratory)  
 Electrical and Electronic Insulation Association (BEAMA Ltd.)  
 GAMBICA (BEAMA Ltd.)  
 Institute of Materials  
 Ministry of Defence  
 Packaging and Industrial Films Association  
 Pira International  
 RAPRA Technology Ltd.

This British Standard, having been prepared under the direction of the Plastics and Rubber Standards Policy Committee, was published under the authority of the Standards Board and comes into effect on 15 January 1994

© BSI 07-1999

The following BSI references relate to the work on this standard:  
 Committee reference PRM/21  
 Draft for comment 91/39043 DC

### Amendments issued since publication

Amd. No.	Date	Comments
8633	July 1996	Indicated by a sideline in the margin

ISBN 0 580 22700 6

# Contents

	Page
Committees responsible	Inside front cover
National foreword	ii
<hr/>	
Foreword	2
1 Scope	3
2 Normative references	3
3 Principle	3
4 Definitions	3
5 Apparatus	5
6 Test specimens	6
7 Number of test specimens	6
8 Conditioning	6
9 Procedure	6
10 Calculation and expression of results	7
11 Precision	8
12 Test report	8
<hr/>	
Annex A (informative) Young's modulus and related values	10
Figure 1 — Typical stress/strain curves	9
<hr/>	
Table 1 — Recommended testing speeds	5
<hr/>	
List of references	Inside back cover

## National foreword

This British Standard has been prepared by Technical Committee PRI/21 and is the English language version of EN ISO 527-1:1996 *Plastics — Determination of tensile properties — Part 1: General principles* published by the European Committee for Standardization (CEN). It is identical with ISO 527-1:1993 including Corr 1:1994 published by the International Organization for Standardization (ISO).

### Cross-references

International standard	Corresponding British Standard
ISO 291:1977	BS 2782 <i>Methods of testing plastics</i> Part 0:1992 <i>Introduction</i> (Appendix A is identical)
ISO 2602:1980	BS 2846: <i>Guide to statistical interpretation of data</i> Part 2:1981 <i>Estimation of the mean: confidence interval</i> (Identical)

The Technical Committee has reviewed the provisions of ISO 5893:1985, to which normative reference is made in the text, and has decided that they are acceptable for use in conjunction with this standard.

**WARNING NOTE.** This British Standard, which is identical with ISO 527-1, does not necessarily detail all the precautions necessary to meet the requirements of the Health and Safety at Work etc. Act 1974. Attention should be paid to any appropriate safety precautions and the method should be operated only by trained personnel.

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

**Compliance with a British Standard does not of itself confer immunity from legal obligations.**

### Summary of pages

This document comprises a front cover, an inside front cover, pages i and ii, the EN ISO title page, pages 2 to 10, an inside back cover and a back cover.

This standard has been updated (see copyright date) and may have had amendments incorporated. This will be indicated in the amendment table on the inside front cover.

---

ICS 83.080

Descriptors: See ISO document

English version

## Plastics — Determination of tensile properties — Part 1: General principles

(ISO 527-1:1993 including Corr 1:1994)

Plastiques — Détermination des propriétés en  
traction — Partie 1: Principes généraux  
(ISO 527-1:1993 inclut Corr 1:1994)

Kunststoffe — Bestimmung der  
Zugeigenschaften —  
Teil 1: Allgemeine Grundsätze  
(ISO 527-1:1993 einschließlich Corr 1:1994)

This European Standard was approved by CEN on 1994-12-14. CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

### CEN

European Committee for Standardization  
Comité Européen de Normalisation  
Europäisches Komitee für Normung

Central Secretariat: rue de Stassart 36, B-1050 Brussels

## Foreword

The text of the International Standard from Technical Committee ISO/TC 61, Plastics, of the International Organization for Standardization (ISO) has been taken over as a European Standard by Technical Committee CEN/TC 249, Plastics, the secretariat of which is held by IBN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by August 1996, and conflicting national standards shall be withdrawn at the latest by August 1996.

According to CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

## 1 Scope

**1.1** This part of ISO 527 specifies the general principles for determining the tensile properties of plastics and plastic composites under defined conditions.

Several different types of test specimen are defined to suit different types of material which are detailed in subsequent parts of ISO 527.

**1.2** The methods are used to investigate the tensile behaviour of the test specimens and for determining the tensile strength, tensile modulus and other aspects of the tensile stress/strain relationship under the conditions defined.

**1.3** The methods are selectively suitable for use with the following range of materials:

- rigid and semirigid thermoplastics moulding and extrusion materials, including filled and reinforced compounds in addition to unfilled types; rigid and semirigid thermoplastics sheets and films;
- rigid and semirigid thermosetting moulding materials, including filled and reinforced compounds; rigid and semirigid thermosetting sheets, including laminates;
- fibre-reinforced thermoset and thermoplastics composites incorporating unidirectional or non-unidirectional reinforcements such as mat, woven fabrics, woven rovings, chopped strands, combination and hybrid reinforcements, rovings and milled fibres; sheets made from pre-impregnated materials (prepregs);
- thermotropic liquid crystal polymers.

The methods are not normally suitable for use with rigid cellular materials or sandwich structures containing cellular material.

**1.4** The methods are applied using specimens which may be either moulded to the chosen dimensions or machined, cut or punched from finished and semifinished products such as mouldings, laminates, films and extruded or cast sheet. In some cases a multipurpose test specimen (see ISO 3167:1993, *Plastics — Preparation and use of multipurpose test specimens*), may be used.

**1.5** The methods specify preferred dimensions for the test specimens. Tests which are carried out on specimens of different dimensions, or on specimens which are prepared under different conditions, may produce results which are not comparable. Other factors, such as the speed of testing and the conditioning of the specimens, can also influence the results. Consequently, when comparative data are required, these factors must be carefully controlled and recorded.

## 2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this part of ISO 527. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this part of ISO 527 are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 291:1977, *Plastics — Standard atmospheres for conditioning and testing*.

ISO 2602:1980, *Statistical interpretation of test results — Estimation of the mean — Confidence interval*.

ISO 5893:1985, *Rubber and plastics test equipment — Tensile, flexural and compression types (constant rate of traverse) — Description*.

## 3 Principle

The test specimen is extended along its major longitudinal axis at constant speed until the specimen fractures or until the stress (load) or the strain (elongation) reaches some predetermined value. During this procedure the load sustained by the specimen and the elongation are measured.

## 4 Definitions

For the purposes of this part of ISO 527, the following definitions apply.

**4.1**  
**gauge length,  $L_0$**

initial distance between the gauge marks on the central part of the test specimen; see figures of the test specimens in the relevant part of ISO 527  
it is expressed in millimetres (mm)

**4.2**  
**speed of testing,  $v$**

rate of separation of the grips of the testing machine during the test  
it is expressed in millimetres per minute (mm/min)

**4.3 tensile stress,  $\sigma$  (engineering)**

Tensile force per unit area of the original cross-section within the gauge length, carried by the test specimen at any given moment.  
It is expressed in megapascals (MPa) [see 10.1, equation (3)].

**4.3.1****tensile stress at yield; yield stress,  $\sigma_y$** 

first stress at which an increase in strain occurs without an increase in stress

it is expressed in megapascals (MPa)

it may be less than the maximum attainable stress (see Figure 1, curves b and c)

**4.3.2****tensile stress at break,  $\sigma_B$** 

the tensile stress at which the test specimen ruptures (see Figure 1)

it is expressed in megapascals (MPa)

**4.3.3****tensile strength,  $\sigma_M$** 

maximum tensile stress sustained by the test specimen during a tensile test (see Figure 1)

it is expressed in megapascals (MPa)

**4.3.4****tensile stress at  $x$  % strain (see 4.4),  $\sigma_x$** 

stress at which the strain reaches the specified value  $x$  expressed in percentage

it is expressed in megapascals (MPa)

it may be measured for example if the stress/strain curve does not exhibit a yield point (see Figure 1, curve d). In this case,  $x$  shall be taken from the relevant product standard or agreed upon by the interested parties. However,  $x$  must be lower than the strain corresponding to the tensile strength, in any case

**4.4 tensile strain,  $\varepsilon$** 

Increase in length per unit original length of the gauge.

It is expressed as a dimensionless ratio, or in percentage (%) [see 10.2, equations (4) and (5)].

It is used for strains up to yield point (see 4.3.1); for strains beyond yield point see 4.5.

**4.4.1****tensile strain at yield,  $\varepsilon_y$** 

tensile strain at the yield stress (see 4.3.1 and Figure 1, curves b and c)

it is expressed as a dimensionless ratio, or in percentage (%)

**4.4.2****tensile strain at break,  $\varepsilon_B$** 

tensile strain at the tensile stress at break (see 4.3.2), if it breaks without yielding (see Figure 1, curves a and d)

it is expressed as a dimensionless ratio, or in percentage (%)

for breaking after yielding, see 4.5.1

**4.4.3****tensile strain at tensile strength,  $\varepsilon_M$** 

tensile strain at the point corresponding to tensile strength (see 4.3.3), if this occurs without or at yielding (see Figure 1, curves a and d)

it is expressed as a dimensionless ratio or in percentage (%)

for strength values higher than the yield stress, see 4.5.2

**4.5 nominal tensile strain,  $\varepsilon_t$** 

Increase in length per unit original length of the distance between grips (grip separation).

It is expressed as a dimensionless ratio, or in percentage (%) [see 10.2, equations (6) and (7)].

It is used for strains beyond yield point (see 4.3.1). For strains up to yield point, see 4.4. It represents the total relative elongation which takes place along the free length of the test specimen.

**4.5.1****nominal tensile strain at break,  $\varepsilon_{tB}$** 

nominal tensile strain at the tensile stress at break (see 4.3.2), if the specimen breaks after yielding (see Figure 1, curves b and c)

it is expressed as a dimensionless ratio, or in percentage (%)

for breaking without yielding, see 4.4.2

**4.5.2****nominal tensile strain at tensile strength,  $\varepsilon_{tM}$** 

nominal tensile strain at tensile strength (see 4.3.3), if this occurs after yielding (see Figure 1, curve b)

it is expressed as a dimensionless ratio, or in percentage (%)

for strength values without or at yielding, see 4.4.3

**4.6****modulus of elasticity in tension; Young's modulus,  $E_t$** 

ratio of the stress difference  $\sigma_2$  minus  $\sigma_1$  to the corresponding strain difference values  $\varepsilon_2 = 0,0025$  minus  $\varepsilon_1 = 0,0005$  (see Figure 1, curve d and 10.3, equation (8))

it is expressed in megapascals, (MPa)

this definition does not apply to films and rubber

NOTE 1 With computer-aided equipment, the determination of the modulus  $E_t$  using two distinct stress/strain points can be replaced by a linear regression procedure applied on the part of the curve between these mentioned points.

#### 4.7

##### poisson's ratio, $\mu$

negative ratio of the tensile strain  $\varepsilon_n$  in one of the two axes normal to the direction of pull, to the corresponding strain  $\varepsilon$  in the direction of pull, within the initial linear portion of the longitudinal versus normal strain curve

it is expressed as a dimensionless ratio

poisson's ratio is indicated as  $\mu_b$  (width direction) or  $\mu_h$  (thickness direction) according to the relevant axis. Poisson's ratio is preferentially used for long-fibre-reinforced materials

## 5 Apparatus

### 5.1 Testing machine

#### 5.1.1 General

The machine shall comply with ISO 5893, and meet the specifications given in 5.1.2 to 5.1.5, as follows.

#### 5.1.2 Speeds of testing

The tensile-testing machine shall be capable of maintaining the speeds of testing (see 4.2) as specified in Table 1.

**Table 1 — Recommended testing speeds**

Speed mm/min	Tolerance %
1	$\pm 20^a$
2	$\pm 20^a$
5	$\pm 20$
10	$\pm 20$
20	$\pm 10$
50	$\pm 10$
100	$\pm 10$
200	$\pm 10$
500	$\pm 10$

<sup>a</sup> These tolerances are smaller than those indicated in ISO 5893.

#### 5.1.3 Grips

Grips for holding the test specimen shall be attached to the machine so that the major axis of the test specimen coincides with the direction of pull through the centreline of the grip assembly. This can be achieved, for example, by using centring pins in the grips. The test specimen shall be held such that slip relative to the grips is prevented as far as possible and this shall preferably be effected with the type of grip that maintains or increases pressure on the test specimen as the force applied to the test specimen increases. The clamping system shall not cause premature fracture at the grips.

#### 5.1.4 Load indicator

The load indicator shall incorporate a mechanism capable of showing the total tensile load carried by the test specimen when held by the grips. The mechanism shall be essentially free from inertia lag at the specified rate of testing, and shall indicate the load with an accuracy of at least 1 % of the actual value. Attention is drawn to ISO 5893.

#### 5.1.5 Extensometer

The extensometer shall comply with ISO 5893. It shall be capable of determining the relative change in the gauge length on the test specimen at any time during the test. It is desirable, but not essential, that this instrument should automatically record this change. The instrument shall be essentially free from inertia lag at the specified speed of testing, and shall be capable of measuring the change of gauge length with an accuracy of 1 % of the relevant value or better. This corresponds to  $\pm 1 \mu\text{m}$  for the measurement of the modulus, based on a gauge length of 50 mm.

When an extensometer is attached to the test specimen, care shall be taken to ensure that any distortion of or damage to the test specimen is minimal. It is essential that there is no slippage between the extensometer and the test specimen.

The specimens may also be instrumented with longitudinal strain gauges, the accuracy of which shall be 1 % of the relevant value or better. This corresponds to a strain accuracy of  $20 \times 10^{-6}$  (20 microstrain) for the measurement of the modulus. The gauges, surface preparation and bonding agents should be chosen to exhibit adequate performance on the subject material.

### 5.2 Devices for measuring width and thickness of the test specimens

#### 5.2.1 Rigid materials

A micrometer or its equivalent, capable of reading to 0.02 mm or less and provided with means for measuring the thickness and width of the test specimens, shall be used. The dimensions and shape of the anvils shall be suitable for the specimens being measured and shall not exert a force on the specimen such as to detectably alter the dimension being measured.

#### 5.2.2 Flexible materials

A dial-gauge, capable of reading to 0.02 mm or less and provided with a flat circular foot which applies a pressure of  $20 \text{ kPa} \pm 3 \text{ kPa}$ , shall be used for measuring the thickness.

## 6 Test specimens

### 6.1 Shape and dimensions

See that part of ISO 527 relevant to the material being tested.

### 6.2 Preparation of specimens

See that part of ISO 527 relevant to the material being tested.

### 6.3 Gauge marks

If optical extensometers are used, especially for thin sheet and film, gauge marks on the specimen are necessary to define the gauge length. These shall be approximately equidistant from the midpoint, and the distance between the marks shall be measured to an accuracy of 1 % or better.

Gauge marks shall not be scratched, punched or impressed upon the test specimen in any way that may damage the material being tested. It must be ensured that the marking medium has no detrimental effect on the material being tested and that, in the case of parallel lines, they are as narrow as possible.

### 6.4 Checking the test specimens

The specimens shall be free of twist and shall have mutually perpendicular pairs of parallel surfaces. The surfaces and edges must be free from scratches, pits, sink marks and flash. The specimens shall be checked for conformity with these requirements by visual observation against straightedges, squares and flat plates, and with micrometer calipers. Specimens showing observed or measured departure from one or more of these requirements shall be rejected or machined to proper size and shape before testing.

### 6.5 Anisotropy

See that part ISO 527 relevant to the material being tested.

## 7 Number of test specimens

7.1 A minimum of five test specimens shall be tested for each of the required directions of testing and for the properties considered (modulus of elasticity, tensile strength etc.). The number of measurements may be more than five if greater precision of the mean value is required. It is possible to evaluate this by means of the confidence interval (95 % probability, see ISO 2602).

7.2 Dumb-bell specimens that break within the shoulders or the yielding of which spreads to the width of the shoulders shall be discarded and further specimens shall be tested.

7.3 Data from parallel-sided specimens where jaw slippage occurs, or where failure occurs within 10 mm of either jaw, or where an obvious fault has resulted in premature failure, shall not be included in the analysis. Repeat tests shall be carried out on new test specimens.

Data, however variable, shall not be excluded from the analysis for any other reason, as the variability in such data is a function of the variable nature of the material being tested.

NOTE 2 When the majority of failures falls outside the criteria for an acceptable failure, the data may be analysed statistically, but it should be recognized that the final result is likely to be conservative. In such instances, it is preferable for the tests to be repeated with the dumb-bell specimens to reduce the possibility of unacceptable results.

## 8 Conditioning

The test specimen shall be conditioned as specified in the appropriate standard for the material concerned. In the absence of this information, the most appropriate condition from ISO 291 shall be selected, unless otherwise agreed upon by the interested parties.

## 9 Procedure

### 9.1 Test atmosphere

Conduct the test in the same atmosphere used for conditioning the test specimen, unless otherwise agreed upon by the interested parties, e.g. for testing at elevated or low temperatures.

### 9.2 Dimensions of test specimen

Measure the width  $b$  to the nearest 0.1 mm and the thickness  $h$  to the nearest 0.02 mm at the centre of each specimen and within 5 mm of each end of the gauge length.

Record the minimum and maximum values for width and thickness of each specimen and make sure that they are within the tolerances indicated in the standard applicable for the given material.

Calculate the arithmetic means for the width and thickness of each specimen, which shall be used for calculation purposes.

NOTE 3 In the case of injection-moulded specimens, it is not necessary to measure the dimensions of each specimen. It is sufficient to measure one specimen from each lot to make sure that the dimensions correspond to the specimen type selected (see the relevant part of ISO 527). With multiple-cavity moulds, ensure that the dimensions of the specimens are the same for each cavity.

NOTE 4 For test specimens stamped from sheet or film material, it is permissible to assume that the mean width of the central parallel portion of the die is equivalent to the corresponding width of the specimen. The adoption of such a procedure should be based on comparative measurements taken at periodic intervals.

### 9.3 Clamping

Place the test specimen in the grips, taking care to align the longitudinal axis of the test specimen with the axis of the testing machine. To obtain correct alignment when centring pins are used in the grips, it is necessary to tension the specimen only slightly before tightening the grips (see 9.4). Tighten the grips evenly and firmly to avoid slippage of the test specimen.

### 9.4 Prestresses

The specimen shall not be stressed substantially prior to test. Such stresses can be generated during centring of a film specimen, or can be caused by the clamping pressure, especially with less rigid materials.

The residual stress  $\sigma_0$  at the start of a test shall not exceed the following value, for modulus measurement:

$$|\sigma_0| \leq 5 \times 10^{-4} E_t \quad \dots (1)$$

which corresponds to a prestrain of  $\varepsilon_0 \leq 0.05\%$ , and for measuring relevant stresses  $\sigma$ , e.g.  $\sigma = \sigma_y$ ,  $\sigma_M$  or  $\sigma_B$ :

$$\sigma_0 \leq 10^{-2} \sigma \quad \dots (2)$$

### 9.5 Setting of extensometers

After balancing the prestresses, set and adjust a calibrated extensometer to the gauge length of the test specimen, or provide longitudinal strain gauges, in accordance with 5.1.5. Measure the initial distance (gauge length) if necessary. For the measurement of Poisson's ratio, two elongation- or strain-measuring devices shall be provided to act in the longitudinal and normal axes simultaneously.

For optical measurements of elongation, place gauge marks on the specimen in accordance with 6.3.

The elongation of the free length of the test specimen, measured from the movement of the grips, is used for the values of the nominal tensile strain  $\varepsilon_t$  (see 4.5).

### 9.6 Testing speed

Set the speed of testing in accordance with the appropriate standard for the material concerned. In the absence of this information, the speed of testing should be agreed between the interested parties in accordance with Table 1.

It may be necessary or desirable to adopt different speeds for the determination of the elastic modulus, of the stress/strain properties up to the yield point, and for the measurement of tensile strength and maximum elongation. For each testing speed, separate specimens shall be used.

For the measurement of the modulus of elasticity, the selected speed of testing shall provide a strain rate as near as possible to 1 % of the gauge length per minute. The resulting testing speed for different types of specimens is given in that part of ISO 527 relevant to the material being tested.

### 9.7 Recording of data

Record the force and the corresponding values of the increase of the gauge length and of the distance between grips during the test. It is preferable to use an automatic recording system which yields complete stress/strain curves for this operation [see clause 10, equations (3), (4) and (5)].

Determine all relevant stresses and strains defined in clause 4 from the stress/strain curve (see Figure 1), or using other suitable means.

For failures outside the criteria for an acceptable failure, see 7.2 and 7.3.

## 10 Calculation and expression of results

### 10.1 Stress calculations

Calculate all stress values defined in 4.3 on the basis of the initial cross-sectional area of the test specimen:

$$\sigma = \frac{F}{A} \quad \dots (3)$$

where

- $\sigma$  is the tensile stress value in question, expressed in megapascals;
- $F$  is the measured force concerned, in newtons;
- $A$  is the initial cross-sectional area of the specimen, expressed in square millimetres.

### 10.2 Strain calculations

Calculate all strain values defined in 4.4 on the basis of the gauge length:

$$\varepsilon = \frac{\Delta L_0}{L_0} \quad \dots (4)$$

$$\varepsilon (\%) = 100 \times \frac{\Delta L_0}{L_0} \quad \dots (5)$$

where

- $\varepsilon$  is the strain value in question, expressed as a dimensionless ratio, or in percentage;
- $L_0$  is the gauge length of the test specimen, expressed in millimetres;
- $\Delta L_0$  is the increase in the specimen length between the gauge marks, expressed in millimetres.

The values of the nominal tensile strain, defined in 4.5, shall be calculated on the basis of the initial distance between the grips:

$$\varepsilon_t = \frac{\Delta L}{L} \quad \dots (6)$$

$$\varepsilon_t (\%) = 100 \times \frac{\Delta L}{L} \quad \dots (7)$$

where

- $\varepsilon_t$  nominal tensile strain, expressed as a dimensionless ratio or percentage, %;
- $L$  initial distance between grips, expressed in millimetres;
- $\Delta L$  increase of the distance between grips, expressed in millimetres.

### 10.3 Modulus calculation

Calculate the modulus of elasticity (Young's modulus), defined in 4.6 on the basis of two specified strain values:

$$E_t = \frac{\sigma_2 - \sigma_1}{\varepsilon_2 - \varepsilon_1} \quad \dots (8)$$

where

- $E_t$  is Young's modulus of elasticity, expressed in megapascals;
- $\sigma_1$  is the stress, in megapascals, measured at the strain value  $\varepsilon_1 = 0,000\ 5$ ;
- $\sigma_2$  is the stress, in megapascals, measured at the strain value  $\varepsilon_2 = 0,002\ 5$ ;

For computer-aided equipment, see 4.6, note 1.

### 10.4 Poisson's ratio

If required, calculate Poisson's ratio defined in 4.7 on the basis of two corresponding strain values perpendicular to each other:

$$\mu_n = -\frac{\varepsilon_n}{\varepsilon} \quad \dots (9)$$

where

- $\mu_n$  is Poisson's ratio, expressed as a dimensionless ratio with  $n = b$  (width) or  $h$  (thickness) indicating the normal direction chosen;
- $\varepsilon$  is the strain in the longitudinal direction;
- $\varepsilon_n$  is the strain in the normal direction, with  $n = b$  (width) or  $h$  (thickness).

### 10.5 Statistical parameters

Calculate the arithmetic means of the test results and, if required, the standard deviations and the 95 % confidence intervals of the mean values according to the procedure given in ISO 2602.

### 10.6 Significant figures

Calculate the stresses and the modulus to three significant figures. Calculate the strains and Poisson's ratio to two significant figures.

## 11 Precision


See that part of ISO 527 relevant to the material being tested.

## 12 Test report

The test report shall include the following information:

- a reference to the relevant part of ISO 527;
- all the data necessary for identification of the material tested, including type, source, manufacturer's code number and history, where these are known;
- description of the nature and form of the material in terms of whether it is a product, semifinished product, test panel or specimen. It should include the principal dimensions, shape, method of manufacture, succession of layers and any pretreatment;
- type of test specimen, the width and thickness of the parallel section, including mean, minimum and maximum values;
- method of preparing the test specimens, and any details of the manufacturing method used;
- if the material is in product or semifinished product form, the orientation of the specimen in relation to the product or semifinished product from which it is cut;
- number of test specimens tested;
- standard atmosphere for conditioning and testing, plus any special conditioning treatment, if required by the relevant standard for the material or product concerned;

- i) accuracy grading of the test machine (see ISO 5893);
- j) type of elongation or strain indicator;
- k) type of clamping device and clamping pressure, if known;
- l) testing speeds;
- m) individual test results;
- n) mean value(s) of the measured property(ies), quoted as the indicative value(s) for the material tested;
- o) standard deviation, and/or coefficient of variation, and/or confidence limits of the mean, if required;
- p) statement as to whether any test specimens have been rejected and replaced, and, if so, the reasons;
- q) date of measurement.

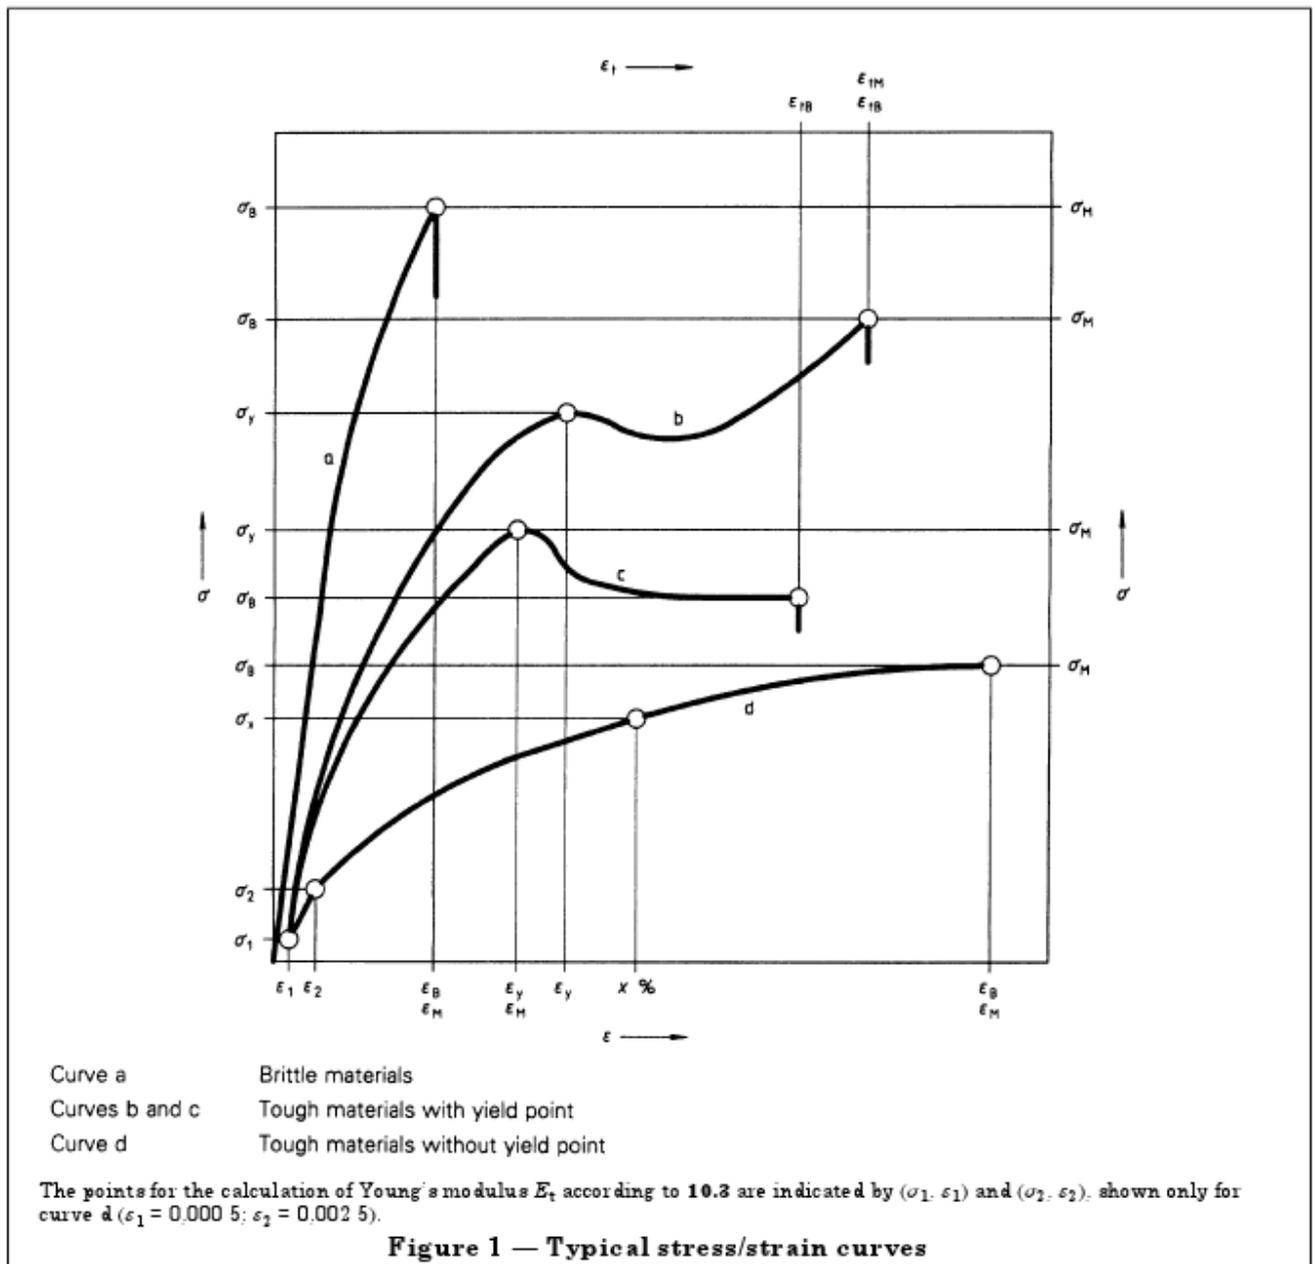

## Annex A (informative) Young's modulus and related values

Due to their viscoelastic behaviour many properties of polymer materials depend not only on temperature but also on time. With regard to the tensile test, this causes nonlinear stress/strain curves (bending towards the strain axis) even within the range of linear viscoelasticity. This effect is pronounced in the case of tough polymers. Consequently, the values of the tangent modulus of tough materials taken from the initial part of the stress/strain curves often depend strongly on the scales used. Thus the conventional method (tangent at the initial point of the stress/strain curve) does not give reliable moduli for these materials.

The method for the measurement of Young's modulus prescribed in this part of ISO 527 is based, therefore, on two specified strain values, i.e. 0.25 % and 0.05 %. (The lower strain value has been set at not zero in order to avoid errors in the measured modulus caused by possible onset effects at the beginning of the stress/strain curve.)

In the case of brittle polymers, both the new and the conventional methods give the same values for the modulus. The new method, however, allows accurate and reproducible measurement of the moduli of tough plastics. The definition of the initial tangent modulus, therefore, has been deleted in the present part of ISO 527.

The aspects mentioned above for the modulus similarly relate to the "offset yield point" which in ISO/R 527 was defined by the deviation of the stress/strain curve from its initial linearity. The offset yield point, therefore, is replaced by a point of specified strain (stress at  $x$  % strain,  $\sigma_x$ , see 4.3.4). Since the definition of such a "substitute" yield point is significant for tough materials only, the specified strain shall be chosen near the yield strain commonly found.

## List of references

See national foreword.

**BS EN ISO  
527-1:1996  
BS 2782-3:  
Method 321:  
1994  
ISO 527-1:  
1993**

---

---

## **BSI — British Standards Institution**

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

### **Revisions**

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover.  
Tel: 020 8996 9000. Fax: 020 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

### **Buying standards**

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: 020 8996 9001. Fax: 020 8996 7001.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

### **Information on standards**

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre.  
Tel: 020 8996 7111. Fax: 020 8996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration.  
Tel: 020 8996 7002. Fax: 020 8996 7001.

### **Copyright**

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

If permission is granted, the terms may include royalty payments or a licensing agreement. Details and advice can be obtained from the Copyright Manager.  
Tel: 020 8996 7070.

BSI  
389 Chiswick High Road  
London  
W4 4AL